



# Resilient Moduli of Granular Base Materials Using a Modified Type 5 Gradation

Prepared by Missouri  
University of Science and  
Technology and Missouri  
Department of Transportation

**TECHNICAL REPORT DOCUMENTATION PAGE.**

|   |  |  |            |
|---|--|--|------------|
| 1. Report No.:  | 2. Government Accession No.:                                 | 3. Recipient's Catalog No.:  |            |
| 4. Title and Subtitle:<br><b>Resilient Moduli of Granular Base Materials<br/>Using a Modified Type 5 Gradation</b>  |  | 5. Report Date: January 2009   |            |
|   |  | 6. Performing Organization Code:   |            |
| 7. Author(s): Dr. David Richardson, Steven M. Lusher  |  | 8. Performing Organization Report No.: OR09-015  |            |
| 9. Performing Organization Name and Address:<br>Missouri University of Science & Technology<br>Department of Civil, Architectural, and Environmental Engineering<br>211 Butler-Carlton Hall, Rolla, MO 65409  |  | 10. Work Unit No.:   |            |
|   |  | 11. Contract or Grant No.:<br>RI08-021   |            |
| 12. Sponsoring Agency Name and Address:<br><br>Missouri Department of Transportation<br>Organizational Results<br>PO BOX 270, JEFFERSON CITY MO 65102   |  | 13. Type of Report and Period Covered:<br><br>Final Report.  |            |
|   |  | 14. Sponsoring Agency Code:  |            |
| 15. Supplementary Notes:<br>The investigation was conducted in cooperation with the U. S. Department of Transportation, Federal Highway Administration.   |  |  |            |
| 16. Abstract:<br>The Missouri Department of Transportation (MoDOT) in collaboration with the Missouri Limestone Producers Association (MLPA) was interested in determining what effect a change in the Type 5 aggregate base gradation specification would have on the resilient modulus ( $M_r$ ) of said aggregate. The proposed change would lower the minimum allowable total percentage of material passing the #4 (4.75 mm mesh) sieve from 35% to 25%, and the #30 (0.600 mm mesh) sieve from 10% to 5%. The remainder of the gradation specification would remain unchanged. The rationale for this proposed change is that some aggregate producers believe the change could help lower their costs of producing a Type 5 aggregate base material.<br>To investigate the proposed gradation specification change, an experimental gradation was devised which followed the lower bounds of the proposed gradation specification on the #4, #30, and #200 sieves, and approximated the as-delivered gradations of two aggregate formations previously tested for MoDOT on the 3/8, 1/2, 3/4, and 1 inch sieves, making it a relatively open-graded material. Thus, two different aggregate sources were tested.<br>In the previous study for MoDOT, two gradations were analyzed: as-delivered Type 5 materials, and gradations with elevated fines contents. Both gradations could be considered to be high-fines content materials, with minus #200 contents between 11 and 18%. As a result of changing the gradation to fit the lower proposed specification limits, the experimental gradation in the present study contained no minus #200 material, and had significantly more #4 retained material, but less #8 retained material. The resulting $M_r$ values in this study were greater than the results from the previous study for the same aggregates. Besides a change in gradation, the degrees of saturation for the proposed, more open-graded gradation were significantly lower than seen in the previous study for the same aggregate types. |  |  |            |
| 17. Key Words:<br>Resilient Modulus, Mechanistic-Empirical Pavement Design Guide (M-E PDG), AASHTO T 307, Unbound Granular Base   |  | 18. Distribution Statement:<br>No restrictions. This document is available to the public through National Technical Information Center, Springfield, Virginia 22161. |            |
| 19. Security Classification (of this report):<br>Unclassified.  | 20. Security Classification (of this page):<br>Unclassified. | 21. No of Pages:<br>40   | 22. Price: |

**FINAL REPORT  
RI08-021**

**Resilient Moduli of Granular Base Materials  
Using a Modified Type 5 Gradation**

Prepared for the

Missouri Department of Transportation  
Organizational Results

By

David N. Richardson, PE  
Steven M. Lusher, EIT  
Missouri University of Science and Technology  
(Formerly University of Missouri-Rolla)

January 2009

The opinions, findings, and conclusions expressed in this report are those of the principal investigator and the Missouri Department of Transportation. This report does not constitute a standard, specification, or regulation.

## ACKNOWLEDGEMENTS

The authors wish to thank the Missouri Department of Transportation (MoDOT) for sponsoring this work and John Donahue for coordination and support.

## EXECUTIVE SUMMARY

The Missouri Department of Transportation (MoDOT) in collaboration with the Missouri Limestone Producers Association (MLPA) was interested in determining what effect a change in the Type 5 aggregate base gradation specification would have on the resilient modulus ( $M_r$ ) of said aggregate. The proposed change would lower the minimum allowable total percentage of material passing the #4 (4.75 mm mesh) sieve from 35% to 25%, and the #30 (0.600 mm mesh) sieve from 10% to 5%. The remainder of the gradation specification would remain unchanged. The rationale for this proposed change is that some aggregate producers believe the change could help lower their costs of producing a Type 5 aggregate base material.

To investigate the proposed gradation specification change, an experimental gradation was devised which followed the lower bounds of the proposed gradation specification on the #4, #30, and #200 sieves, and approximated the as-delivered gradations of two aggregates previously tested for MoDOT on the 3/8, 1/2, 3/4, and 1 inch sieves, making it a relatively open-graded material. Two different aggregate sources were tested.

$M_r$ , a material stiffness characterization test, was determined in accordance with the American Association of State Highway and Transportation Officials (AASHTO) test method T 307-99 (2003), "Determining the Resilient Modulus of Soils and Aggregate Materials." MoDOT contracted with Missouri S&T to test three replicate specimens per aggregate type according to T 307. Target dry unit weights and moisture contents at which to prepare the  $M_r$  specimens were determined through reviewing the literature and some trial and error testing.

In the previous study for MoDOT, two gradations were analyzed: as-delivered Type 5 materials, and gradations with elevated fines contents. Both gradations could be considered to be high-fines content materials, with minus #200 contents between 11 and 18%. As a result of changing the gradation to fit the lower proposed specification limits, the experimental gradation in the present study contained no minus #200 material, and had significantly more #4 retained material, but less #8 retained material. The resulting  $M_r$  values in this study were greater than the results from the previous study for the same aggregates. Besides a change in gradation, the degrees of saturation for the proposed, more open-graded gradation were significantly lower than seen in the previous study for the same aggregate types.

## TABLE OF CONTENTS

|  |     |
|--|-----|
| ACKNOWLEDGEMENTS .....                             | II  |
| EXECUTIVE SUMMARY .....                            | II  |
| TABLE OF CONTENTS .....                            | III |
| LIST OF FIGURES .....                              | V   |
| LIST OF TABLES .....                               | VI  |
| INTRODUCTION .....                                 | 1   |
| OBJECTIVES .....                                   | 3   |
| TECHNICAL APPROACH .....                           | 4   |
| General .....                                      | 4   |
| Materials .....                                    | 4   |
| Target Resilient Modulus Specimen Properties ..... | 4   |
| Gradation .....                                    | 4   |
| Dry Unit Weight and Moisture Content .....         | 6   |
| Resilient Modulus Testing .....                    | 10  |
| Equipment .....                                    | 10  |
| Specimen Fabrication .....                         | 11  |
| Stress States/Testing Sequence .....               | 12  |
| Testing Procedure .....                            | 12  |
| RESULTS AND DISCUSSION .....                       | 14  |
| Compaction Parameters .....                        | 14  |
| Regression Coefficients .....                      | 14  |
| Quality of the Testing Program .....               | 15  |
| Effect of Gradation on $M_r$ .....                 | 16  |
| Optimum Fines Content .....                        | 20  |

|  |    |
|--|----|
| Comparison to Past Studies .....                                   | 21 |
| Constructibility .....   | 23 |
| Comparison of Experimental Gradations to Other DOT Gradations..... | 24 |
| CONCLUSIONS.....   | 27 |
| RECOMMENDATIONS – FUTURE RESEARCH .....                            | 28 |
| REFERENCES .....   | 29 |
| APPENDIX A .....   | 32 |
| APPENDIX B .....   | 35 |

## LIST OF FIGURES

|  |    |
|--|----|
| Figure 1: Histogram of Percent Fines for Type 5 Aggregate Used Statewide .....             | 2  |
| Figure 2: Gradation Summary .....  | 5  |
| Figure 3: Individual Percent Retained Gradations .....                                     | 6  |
| Figure 4: Triaxial Chamber and Measurement Devices .....                                   | 10 |
| Figure 5: Bethany Falls; Pooled $M_r$ vs $\theta$ ; O-G, A-D, and W-F Gradations.....      | 18 |
| Figure 6: Bethany Falls; Pooled $M_r$ vs $\tau_{oct}$ ; O-G, A-D, and W-F Gradations ..... | 18 |
| Figure 7: Gasconade; Pooled $M_r$ vs $\theta$ ; O-G, A-D, and W-F Gradations .....         | 19 |
| Figure 8: Gasconade; Pooled $M_r$ vs $\tau_{oct}$ ; O-G, A-D, and W-F Gradations .....     | 19 |
| Figure 9: $M_r$ (at $\theta = 12$ psi) versus P200 .....                                   | 20 |
| Figure 10B: BF O-G1 $M_r$ Data, Eq. 1 Regression Results, & Eq. 2 Plot.....                | 35 |
| Figure 11B: BF O-G2 $M_r$ Data, Eq. 1 Regression Results, & Eq. 2 Plot.....                | 36 |
| Figure 12B: BF O-G3 $M_r$ Data, Eq. 1 Regression Results, & Eq. 2 Plot.....                | 37 |
| Figure 13B: Gasc O-G1 $M_r$ Data, Eq. 1 Regression Results, & Eq. 2 Plot.....              | 38 |
| Figure 14B: Gasc O-G2 $M_r$ Data, Eq. 1 Regression Results, & Eq. 2 Plot.....              | 39 |
| Figure 15B: Gasc O-G3 $M_r$ Data, Eq. 1 Regression Results, & Eq. 2 Plot.....              | 40 |


## LIST OF TABLES

|  |    |
|--|----|
| Table 1: Project Materials .....                                       | 4  |
| Table 2: Total and Effective Moisture Contents .....                   | 9  |
| Table 3: Testing Sequence for Granular Base Material .....             | 12 |
| Table 4: Summary of Results .....                                      | 15 |
| Table 5: Replicate One-Way Anova .....                                 | 16 |
| Table 6: Resilient Moduli at $\theta = 12$ psi .....                   | 17 |
| Table 7: Various State Specifications for Open-Graded Aggregates ..... | 25 |

## INTRODUCTION

The Missouri Department of Transportation (MoDOT) in collaboration with the Missouri Limestone Producers Association (MLPA) was interested in determining what effect a change in the Type 5 aggregate base gradation specification would have on the resilient modulus of said aggregate. The proposed change would lower the minimum allowable total percentage of material passing the #4 (4.75 mm mesh) sieve from 35% to 25%, and the #30 (0.600 mm mesh) sieve from 10% to 5%. The remainder of the gradation specification would remain unchanged. The rationale for this proposed change is that some aggregate producers believe the change could help lower their costs of producing a Type 5 aggregate base material.

MoDOT's Type 5 aggregate base was originally developed to be a more drainable (permeable) base material when compared with MoDOT's Type 1 aggregate base. Currently, the only difference in gradation specifications between a Type 5 and a Type 1 aggregate base material is that there is an upper limit on the amount of fines (i.e. that material that passes the #200 or 0.074 mm mesh sieve) that can be present in a Type 5 material. However, with a current upper limit of 15% fines, many of the Type 5 stockpiles around the state contain material that is essentially non-drainable when used as a pavement base aggregate. Figure 1 is a histogram showing the percent passing the #200 sieve (P200) for Type 5 base aggregates used in Missouri in the recent past. The data supplied by MoDOT represents 1811 gradation analyses that reported a P200 value.

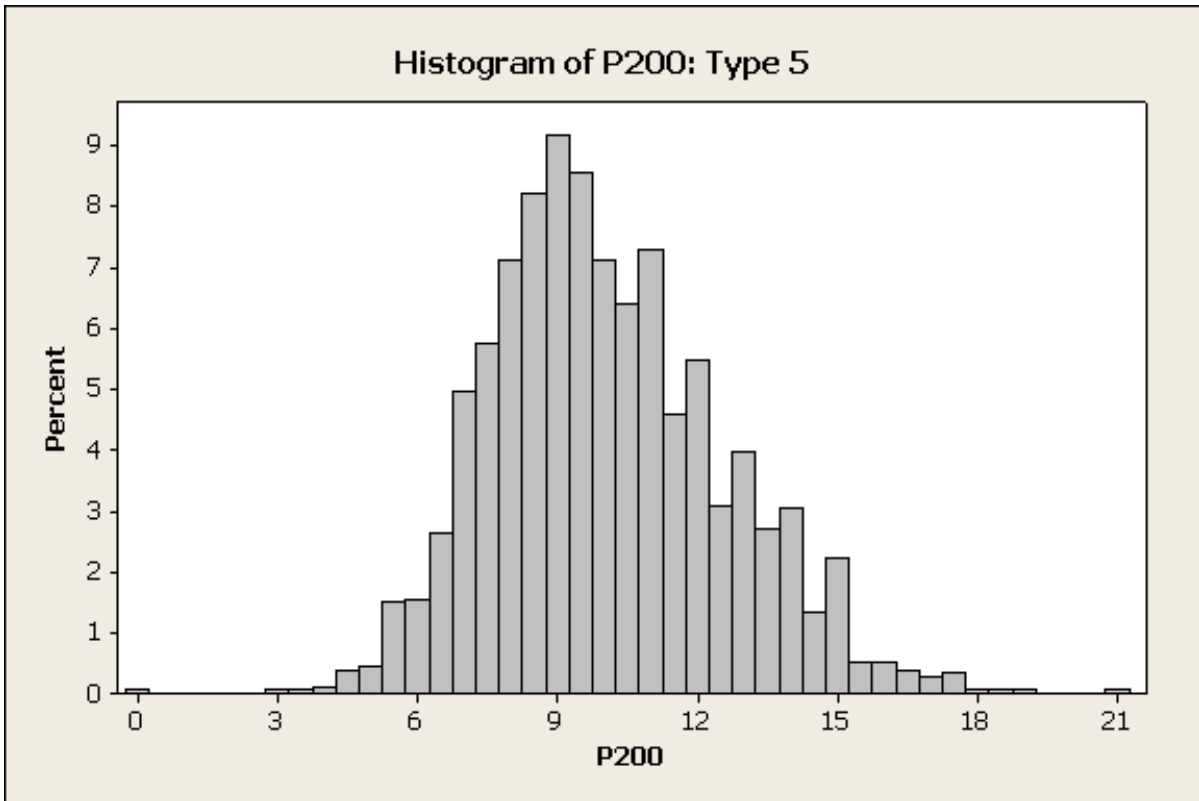

**Figure 1: Histogram of Percent Fines for Type 5 Aggregate Used Statewide**

The median value for the data depicted in Figure 1 is 9.7% fines with the mean being 10.0% fines. The majority of the data exceeds 6% fines. This data hardly represents a drainable material. For those aggregate producers who believe the proposed Type 5 gradation specification change could save them money by reducing some or all aspects of processing a Type 5 material, it seems logical that those producers would also see a lowering of the amount of fines produced for that particular process. This lowering of the fines content could help improve the drainability of that particular Type 5 product.

To investigate the proposed gradation specification change, an experimental gradation was devised which followed the lower bounds of the proposed gradation specification on the #4, #30, and #200 sieves, and approximated the as-delivered gradations of two aggregates previously tested for MoDOT (1) on the 3/8, 1/2, 3/4, and 1 inch sieves, making it a relatively open-graded material. Two different aggregate sources were tested.

The resilient modulus ( $M_r$ ), a material stiffness characterization test, was determined in accordance with the American Association of State Highway and Transportation Officials (AASHTO) test method T 307-99 (2003) (2). MoDOT contracted with Missouri S&T to test three replicate specimens per aggregate type according to test method T 307.

## OBJECTIVES

The objective of this project is to determine the  $M_r$  of the two base aggregates when the gradations are constructed to basically follow the lower bounds of the proposed gradation specification then compare those  $M_r$  to previously determined  $M_r$  for the same aggregates but tested in the as-delivered condition.

## TECHNICAL APPROACH

### General

The technical approach included choice of materials, determination of the gradation, dry unit weight, and moisture content at which to perform  $M_r$  testing, specimen fabrication, and  $M_r$  testing.

### Materials

The two crushed aggregates chosen to be tested were a Gasconade Formation dolomite and a Bethany Falls Formation limestone. Of the five aggregates tested in the previously mentioned  $M_r$  study for MoDOT (1), these two were selected for this project mainly because the wide range in  $M_r$  behavior, coupled with wide differences in Los Angeles Abrasion (LAA = resistance to impact and abrasion) values and absorptions ( $P_a$ ). The LAA values were supplied by MoDOT and the  $P_a$  values were determined during the previous MoDOT  $M_r$  study. Table 1 summarizes the material names, designations used throughout the remainder of this paper, and the LAA and  $P_a$  values.

**Table 1: Project Materials**

| Name                        | Designation | $P_a$ (%) | LAA (%) |
|-----------------------------|-------------|-----------|---------|
| Bethany Falls, as-delivered | BF A-D      | 1.89*     | 24      |
| Bethany Falls, open-graded  | BF O-G      | 1.91**    |         |
| Gasconade, as-delivered     | Gasc A-D    | 3.84*     | 30      |
| Gasconade, open-graded      | Gasc O-G    | 3.80**    |         |

\*Based on testing a combined sample (coarse and fine aggregate) using the CoreLok® method


\*\*Based on AASHTO T 85 (coarse aggregate only) (3)

### Target Resilient Modulus Specimen Properties

#### Gradation


The as-delivered gradations of the Gasconade and Bethany Falls material met the current Type 5 specifications and were fairly similar, especially on those sieve sizes larger than the #4. They also exhibited percent minus #200 values approaching the upper limit of the specification. The experimental gradation used in this study follows the lower bounds of the proposed gradation on the #4, #30, and #200 sieves and is considered open-graded. Because the proposed specification change only applies to the #4 and #30 sieves, the idea was to isolate the effect of the proposed change on  $M_r$  by keeping percentages passing the larger sieve sizes of the two aggregates the same as or similar to the as-delivered gradations, thus keeping any  $M_r$  comparisons between the experimental and as-delivered gradations mostly a function of the minus 3/8 in. portion of the particle size distribution. Figure 2 summarizes the as-

delivered and experimental gradations, and the current and proposed upper and lower specification limits (USL and LSL, respectively).

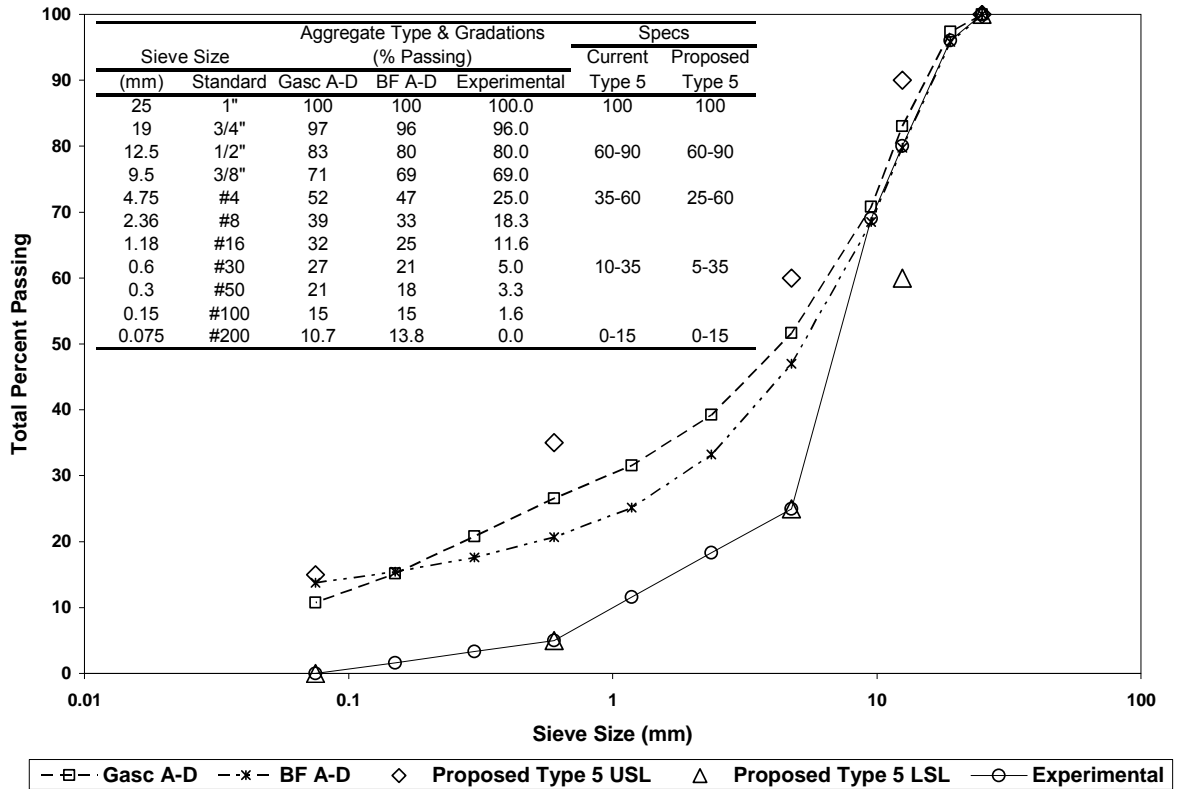

**Figure 2: Gradation Summary**

Figure 3 expresses the gradations in terms of Individual Percent Retained, which more clearly depicts the differences in the gradations. The as-delivered and proposed gradations are essentially the same except the percent #4 retained is greater for the proposed gradation, and the percents retained on the #8 and #200 are less.

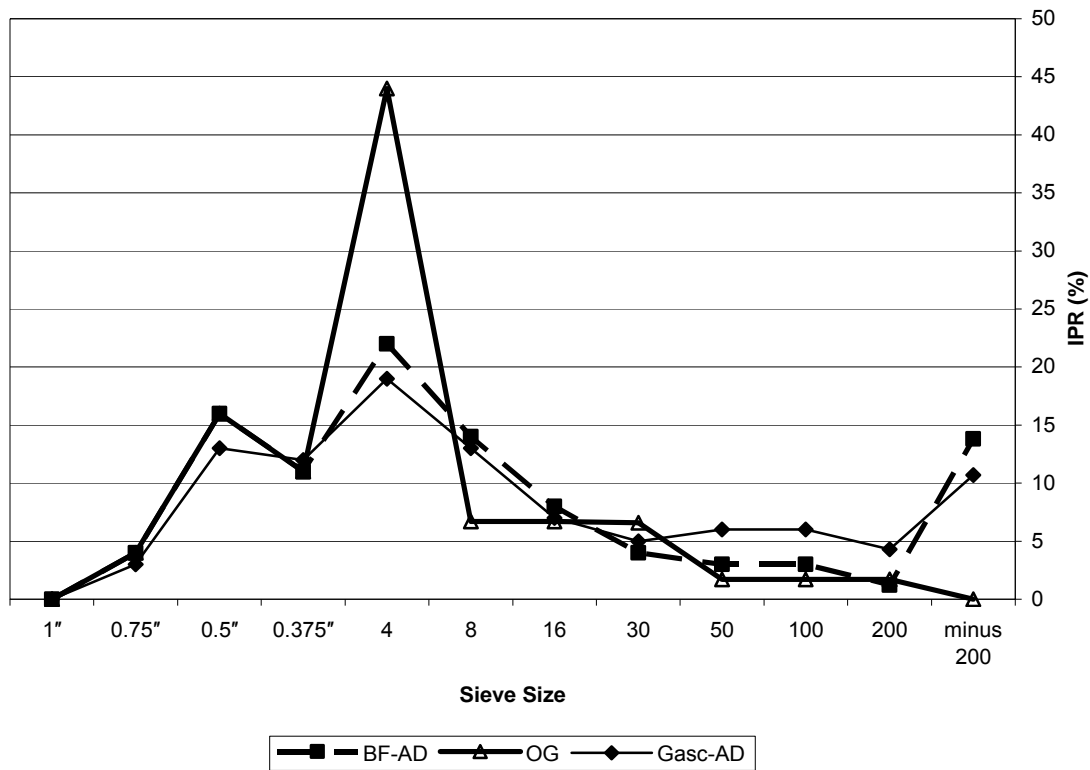

**Figure 3: Individual Percent Retained Gradations**

In order to accurately construct the experimental gradation containing no material passing the #200 sieve, it was necessary to first perform some processing of the as-delivered material. The bagged aggregates were dry-sieved into the different size fractions shown in the table within Figure 2. Each size fraction was then individually washed over the associated sieve and then oven-dried. This process produced washed, oven-dried aggregate fractions that were then re-combined in the appropriate percentages and amounts to build test specimens with the experimental gradation.

#### Dry Unit Weight and Moisture Content

A considerable portion of the work involved determining the dry unit weight and moisture content at which to perform the  $M_r$  testing. Because the experimental gradation was open and cohesionless, the initial thought was to obtain the maximum dry unit weight using American Society of Testing and Materials (ASTM) test method D 4253-00 (4). Within this test specification, there are two basic methods: one using oven-dry aggregate (method 1A) and the other using wet aggregate (method 1B). The decision was made to use method 1B because it was assumed it would result in the densest particle configuration; i.e. a higher dry unit weight. However, because of the wide range of particle sizes in the specimen, major segregation occurred during the test resulting in a non-uniform densification of the aggregate particles; the smaller particles were in the bottom of the mold with the larger particles on top. It

was also assumed that this same phenomenon would have occurred if method 1A had been used. Therefore, the results from ASTM D 4253 were deemed invalid and were not used to determine the specimen conditions for  $M_r$  testing.

It seemed that the logical alternative to ASTM D 4253 for determining the maximum dry unit weight of the experimental gradation was the standard proctor test, AASHTO T 99 (5). Although the use of T 99 for open-graded aggregates can result in no definite moisture-density relationship, it seemed appropriate to try T 99 with the experimental gradation because MoDOT specifies this particular test method for determination of field densities. However, knowing that the highly-drainable nature of the experimental gradation would limit the amount of water that could be added to the material without it simply seeping out of the bottom of the proctor mold, a one-point or single moisture content proctor was investigated.

Having decided to attempt a one-point T 99, the next issue was determining what moisture content to use during compaction. The thought was to look at how other state DOT's that actually specify open-graded, unbound granular material base courses determine what compactive effort/method and moisture content to specify for construction of such base courses.

In a 2004 report published by the Iowa State University Center for Transportation Research and Education (CTRE) in collaboration with the Iowa Department of Transportation (6), results of a survey show that 6 states use permeable bases only, 11 use only dense-graded bases, and 29 states use both permeable and dense-graded bases. However, this survey does not indicate the percentage or number of these permeable bases that are treated (asphalt or cement) or non-treated (unbound) aggregate bases. MoDOT's Type 5 base aggregate is an unbound material. A review of the highway construction specifications of a few of the states listed in the survey as using permeable bases seemed to indicate that very few use unbound, open-graded, permeable bases in pavement construction; most use asphalt or cement treated aggregates.

In the latest on-line-available specifications, special provisions, supplements, etc., Michigan, Oregon, and Wisconsin (and there could be more) do specify unbound, open-graded, permeable bases in pavement construction. Excerpts from these states' specifications are given in Appendix A. It appears that Michigan has replaced a compaction method based on roller-type and roller patterns to a percent compaction determination (7), but has not clearly specified how to determine the reference or maximum dry unit weight (8).

The Oregon specification also indicates a percent compaction of maximum "density" for the dense-graded aggregates and does not directly indicate the method to be used to determine said maximum density. However, in an earlier sub-section, reference is made to T 99 and an optimum moisture content. The amount of water required for the "mix design" is normally 5 to 10%, with a field tolerance of  $\pm 2\%$  (9).

It appears that the use of unbound, open-graded base courses has recently been discontinued in Ohio. However, they do specify using field test sections to determine maximum dry unit weight of unbound granular base materials. The test section method utilized depends on whether or not the aggregate has a definite moisture-density relationship (determined using various optional methods). If there is a definite moisture-density relationship, T 99 is used to determine the optimum moisture content and then the test sections are built at that moisture content and rolled until a maximum dry unit weight is achieved. If there is not a definite moisture-density relationship, test sections are built at various moisture contents (starting at 0 to 3% moisture and increasing by 2% for every test section), rolled until a maximum dry unit weight for each moisture content is achieved, and then the maximum dry unit weight determined for the field testing (essentially, a field proctor curve) is used for base construction purposes (10).

Wisconsin specifies a “standard” compaction method for unbound, open-graded aggregates that is a roller-type and roller-pattern method (11). However, Wisconsin requires laboratory permeability testing on aggregates to be used in open-graded base courses and specifies a target unit weight which is achieved when the material is compacted at 6% moisture content using T-99 Method C (12).

Thus, for the purposes of choosing a unit weight and moisture content for preparation of  $M_r$  specimens, the use of a 6% moisture content seemed reasonable in that, for most base aggregates, absorption would be satisfied and there would be sufficient particle surface moisture for compaction lubrication purposes, but there would not be so much water as to flush the finer fractions during compaction (i.e. segregate the particles). This level of moisture also relates fairly well to one of the recommendations in the CTRE report (6):

“As an alternative to trimming equipment (e.g. Gomaco type), use a motor grader with GPS assisted grading (i.e. stakeless grading control). If trimming equipment must be used, however, ensure that the aggregate is delivered to the site with sufficient water content (7%–10 %) to bind the fines during trimming.”

This recommendation was in response to one of the findings of the CTRE report in that segregation of the open-graded base aggregates was found to occur during trimming of the compacted base course; i.e. the aggregate was too dry during trimming and, thus, the vibration of the trimmer caused the fines to segregate downward leaving coarser aggregate particles on the surface. Therefore, it seems that, for unbound, open-graded base aggregates, there needs to be sufficient moisture in the delivered material to provide lubrication for compaction and “bind the fines” to the coarse aggregate to prevent segregation, but not excessive moisture that would prevent maximum densification or cause segregation to occur due to fluid flow.

Thus, the decision was made to compact the  $M_r$  specimens at 6% moisture and at a dry unit weight determined using T 99, Method D (but with no scalping or removal of any size fraction), also at 6% total moisture. Initially, this strategy worked well for the

Gasc O-G material but not so well for the BF O-G material. The Gasc O-G T 99 test resulted in a dry unit weight of 111.2 lb/ft<sup>3</sup>, with no significant moisture seepage or segregation. M<sub>r</sub> tests on the Gasc O-G material under these conditions were also non-problematic.

The BF O-G T 99 test resulted in a dry unit weight of 112.7 lb/ft<sup>3</sup>, with no visible seepage from the bottom of the proctor mold or major segregation of the compacted aggregate. However, the first BF O-G M<sub>r</sub> test specimen prepared at 6% moisture and 112.7 lb/ft<sup>3</sup> dry unit weight experienced significant loss of moisture through the drainage line of the triaxial cell (~170 ml relative to ~25 ml for all other M<sub>r</sub> tests).

Behavior of unbound granular material in regard to compaction moisture is analogous to that of hot mix asphalt (HMA), i.e. part of the HMA's total binder is absorbed, leaving the balance ("effective binder") to function as the lubricant. Thus, two mixes can have the same total binder content, but different effective binder contents, depending on the absorption of the aggregate. The amount of effective binder dictates, in part, the lubrication and hence the behavior under compaction. Unbound granular base materials act in a similar manner. Two different aggregates, with the same total moisture, can behave differently during compaction if they have significantly different absorptions. The difference between the behavior of the Gasconade and the Bethany Falls aggregates in the M<sub>r</sub> testing, regarding the ability to hold moisture, could be attributed to the difference in their absorptions: the Gasc O-G aggregate has absorption ~2% higher than the BF O-G aggregate. Because total moisture is the sum of absorption and surface ("effective") moisture, the surface moisture of the BF O-G aggregate was also ~2% higher than the Gasc O-G, thus the excessive seepage of the BF O-G. Therefore, to keep the surface moisture of the BF O-G consistent with that of the Gasc O-G, the total moisture content to be used for the BF O-G T 99 test, and subsequently the M<sub>r</sub> test, was lowered to 4.0 %, as shown in Table 2.

**Table 2: Total and Effective Moisture Contents**

| <b>Aggregate</b> | <b>Total Moisture</b> | <b>Absorption</b> | <b>Effective Moisture</b> |
|------------------|-----------------------|-------------------|---------------------------|
| Gasconade        | 6.0                   | 3.8               | 2.2                       |
| Bethany Falls    | 4.0                   | 1.9               | 2.1                       |

Actually, 3.9% was the moisture for the BF O-G specimens content as it was adjusted slightly from 4.0% due to actual post-M<sub>r</sub> test moisture contents. Re-running the T 99 test on the BF O-G aggregate when prepared at a 3.9% moisture content resulted in a dry unit weight of 115.5 lb/ft<sup>3</sup>, an increase from 112.7 lb/ft<sup>3</sup> when compacted at 6% moisture.

Therefore, in summary, the target dry unit weights and as-compacted moisture contents for the M<sub>r</sub> specimens were as follows:

- Gasc O-G dry unit weight = 111.2 lb/ft<sup>3</sup>: 6.0% total moisture content
- BF O-G dry unit weight = 115.5 lb/ft<sup>3</sup>: 3.9% total moisture content.


## Resilient Modulus Testing

### Equipment

The  $M_r$  testing equipment was in conformance with AASHTO T 307-99 (2003) (2) for Type I materials (granular bases), which specifies that test specimens shall be 6 in. in diameter. The equipment consisted of a Geotechnical Consulting and Testing Systems (GCTS) control system, an MTS 858 closed-loop servo-hydraulic load system, a GCTS triaxial chamber capable of housing a 6 in. diameter specimen while subjected to cyclic loads, and a GCTS data acquisition system. Load was measured with an external 2200 lb load cell located between the actuator and the chamber piston rod.

Deformation was measured by two Schaevitz MHR-250 linear variable differential transducers (LVDTs) mounted externally to the cell. The range of the LVDTs was  $\pm 6.35$  mm.

Air was used as the confining fluid. Triaxial cell pressure was controlled manually via a pressure regulator, and measured with a pressure transducer linked to the GCTS data acquisition system. The test setup is shown in Figure 4.

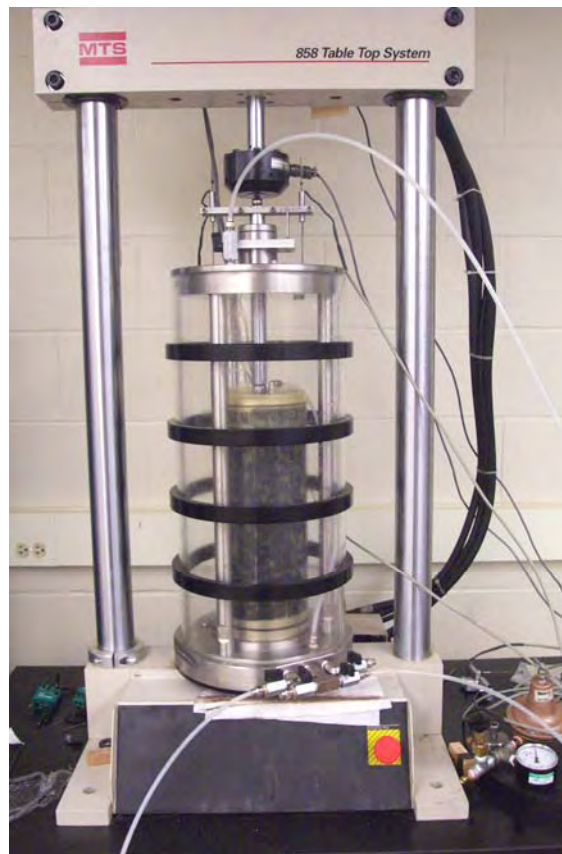

**Figure 4: Triaxial Chamber and Measurement Devices**

## Specimen Fabrication

Knowing the target dry unit weights and moisture contents, the existing moisture content of the material (essentially oven-dry), and the target compacted volume of the specimen, enough material was obtained to produce seven “lifts”; six to be compacted into the mold and one to be used for the as-compacted moisture content determination. The calculated amount of each size fraction necessary to build the experimental gradation was placed into a large pan and water was added to bring the material to the target moisture content plus a small amount to account for moisture loss. After thorough mixing, the aggregate was covered and allowed to cure for at least 15 minutes (usually longer). After curing, a square point scoop was used to systematically remove the calculated amount of moist material from the pan and place it into the mold to be compacted as a lift. After compaction of the six lifts, the remaining material was used for as-compacted moisture content determination.

The specimen mold was 6 in. nominal diameter. The actual compacted specimen diameter was 5.82 in. This met the requirement that the diameter be equal to or greater than five times the maximum particle size, which was 1 in. for the experimental gradation. The material was compacted into the mold using a hand-held mechanical hammer-drill (meeting T 307 specifications) and bearing on a steel plate. An under-compaction principle was utilized to assure uniform compacted density throughout the height of the specimen. This principle requires that the first or bottom lift be under-compacted to some degree (either 1.5 or 2.0% for the material in this study) and each successive lift be decreasingly under-compacted resulting in the top lift thickness being exactly 1/6 of the specimen height. The mold was an aluminum vacuum split mold mounted directly on the triaxial cell pedestal. The specimens were compacted to a height of approximately 11.70 in., which met the requirement of at least two times the specimen diameter.

A 6 in. diameter, 0.025 in. thick latex rubber membrane was placed onto the triaxial cell pedestal and secured with an O-ring. The split mold was then secured onto the pedestal. Sufficient vacuum was applied to the membrane to hold it against the interior mold wall. Prior to adding material to the mold, the membrane was protected from damage during compaction by securing a series of 0.08 in. thick, approximately 2 in. wide, and 12 in. long nitrile rubber strips against the membrane using a small amount of vacuum grease. T 307 specifies membrane thickness between 0.25 and 0.79 mm (0.0098 in. to 0.0311 in.). Because the protective nitrile rubber was cut into strips and placed side-by-side around the interior perimeter of the membrane, it was reasoned that although the combined thickness of the membrane and the rubber nitrile strips exceeded the T 307 specifications, the rubber nitrile strips did not add any confining pressures to the specimen; only the rubber membrane could supply any confining pressure and it met T 307 thickness specifications.

## Stress States/Testing Sequence

Stress state is considered the most important variable that affects the modulus of granular materials. The three principal stresses are  $\sigma_1$ ,  $\sigma_2$ , and  $\sigma_3$ , where  $\sigma_1$  is the major principal stress,  $\sigma_2$  is the intermediate principal stress, and  $\sigma_3$  is the minor principal stress. In a triaxial type test,  $\sigma_1$  is provided by the total vertical stress, and  $\sigma_2$  equals  $\sigma_3$  for a cylindrical specimen. In the triaxial state, the difference between the total vertical stress ( $\sigma_1$ ) and the confining pressure ( $\sigma_3$ ) is called the deviator stress or stress difference ( $\sigma_d$ ). A small static load ( $0.1\sigma_d$ ) provides the “overburden” pressure while the cyclic deviator stress ( $0.9\sigma_d$ ) provides the “vehicle” momentary stress. The sum of the three principal stresses is known as the bulk stress ( $\Theta$ ).

$M_r$  is calculated as  $(0.9\sigma_d)/\epsilon_r$ , where  $\epsilon_r$  is the resilient (recovered) axial strain. For each specimen, resilient modulus was determined at fifteen stress states where confining pressure ranged from 3 to 20 psi and  $\sigma_d$  varied from 3 to 40 psi. This resulted in a range of bulk stress from 12 to 100 psi, which is considered adequate to represent the range in stress states likely to be encountered under field conditions. The testing sequence and stress state schedule is shown in Table 3.

**Table 3: Testing Sequence for Granular Base Material**

| Sequence No. | $\sigma_3$ (psi) | $\sigma_d$ (psi) | $0.9 \sigma_d$ (psi) | $0.1 \sigma_d$ (psi) | $\Theta$ (psi) | No. load applications |
|--------------|------------------|------------------|----------------------|----------------------|----------------|-----------------------|
| 0            | 15               | 15               | 13.5                 | 1.5                  | 60             | 500                   |
| 1            | 3                | 3                | 2.7                  | 0.3                  | 12             | 100                   |
| 2            | 3                | 6                | 5.4                  | 0.6                  | 15             | 100                   |
| 3            | 3                | 9                | 8.1                  | 0.9                  | 18             | 100                   |
| 4            | 5                | 5                | 4.5                  | 0.5                  | 20             | 100                   |
| 5            | 5                | 10               | 9.0                  | 1.0                  | 25             | 100                   |
| 6            | 5                | 15               | 13.5                 | 1.5                  | 30             | 100                   |
| 7            | 10               | 10               | 9.0                  | 1.0                  | 40             | 100                   |
| 8            | 10               | 20               | 18.0                 | 2.0                  | 50             | 100                   |
| 9            | 10               | 30               | 27.0                 | 3.0                  | 60             | 100                   |
| 10           | 15               | 10               | 9.0                  | 1.0                  | 55             | 100                   |
| 11           | 15               | 15               | 13.5                 | 1.5                  | 60             | 100                   |
| 12           | 15               | 30               | 27.0                 | 3.0                  | 75             | 100                   |
| 13           | 20               | 15               | 13.5                 | 1.5                  | 75             | 100                   |
| 14           | 20               | 20               | 18.0                 | 2.0                  | 80             | 100                   |
| 15           | 20               | 40               | 36.0                 | 4.0                  | 100            | 100                   |

## Testing Procedure

The resilient modulus testing procedure involved the following steps: specimen compaction, assembly of the triaxial cell, application of confining pressure, stress conditioning at a given stress state (see stress sequence “zero” in Table 3), and load application through 15 additional stress states. Conditioning was used to eliminate

the effects of any specimen disturbance due to specimen preparation procedures. It also aided in minimizing the effects of initially imperfect contact between end platens and the test specimen. In this study, conditioning load applications were limited to 500 because the decrease in specimen height had ceased by then. Load and deformation data were taken for every load application over the entire sequence of stress states, but only the last five applications were used for calculation of  $M_r$ .

The load duration for each repetition was 0.1 sec followed by 0.9 sec rest. The stress pulse shape was haversine in nature. The drainage valves were left open. Repeated load equipment deflection was determined through the use of an aluminum dummy specimen and was subtracted from total deflections for each stress state. The change in specimen height was continuously monitored. None of the specimens approached the maximum allowable permanent strain of five percent.

To verify that the moisture condition of each of the three replicates tested per aggregate type was substantially the same, moisture contents were obtained on each specimen after the  $M_r$  test had been completed.  $M_r$  test specimens were divided into three approximately equal portions (top, middle, and bottom 4 in.) and moisture contents were determined on each third. Also, moisture contents used for calculation of reported actual (as-tested) dry unit weights were based on the entire specimen. As mentioned previously, for every  $M_r$  specimen, enough material was prepared to produce seven layers or lifts; six to be compacted in the vacuum split mold and one to be used as a check on the as-compacted moisture content. A summary of the target, as-compacted, and actual (post- $M_r$  test) moisture contents, target and actual dry unit weights, and calculated degrees of saturation are given in Table 4 in the Results and Discussion section.

## RESULTS AND DISCUSSION

### Compaction Parameters

Three types of test results were generated during the course of this study: target dry unit weight for  $M_r$  testing (using AASHTO T 99), as-compacted and post- $M_r$  test moisture content, and resilient modulus. T 99 results were presented in the Technical Approach section. Table 4 shows a summary of the target, as-compacted, and actual (post- $M_r$  test) moisture contents, target and actual dry unit weights, and calculated degrees of saturation. As can be seen, the specimens lost very little moisture from drainage during the tests, both aggregate types had about the same effective moisture contents (1.8%), and the actual dry unit weights were very close to the target unit weights. Also included in Table 4 are results for the as-delivered materials that were tested in the previous MoDOT  $M_r$  study (1). The large difference in saturation between the open graded gradations in the present study and the as-delivered gradations in the previous study should be noted. Also shown are the regression coefficients generated from fitting the  $M_r$  data to the constitutive model as described in Part 2 Chapter 2 of the Mechanistic-Empirical Pavement Design Guide (M-E PDG) (13). These will be discussed below.

### Regression Coefficients

Additional information from the testing includes the computation of the regression coefficients ( $k_1, k_2, k_3$ ) which were generated by fitting the  $M_r$  data to the model shown in Eq. 1:

$$M_r = k_1 p_a \left( \frac{\theta}{p_a} \right)^{k_2} \left( \frac{\tau_{oct}}{p_a} + 1 \right)^{k_3} \quad (1)$$

Where

$M_r$  = resilient modulus, psi

$\theta$  = bulk stress =  $\sigma_1 + \sigma_2 + \sigma_3$ , psi

$\sigma_1$  = major principal stress, psi

$\sigma_2$  = intermediate principal stress =  $\sigma_3$  for  $M_r$  test on cylindrical specimen, psi

$\sigma_3$  = minor principal stress/confining pressure, psi

$\tau_{oct}$  = octahedral shear stress =  $\frac{1}{3} \sqrt{(\sigma_1 - \sigma_2)^2 + (\sigma_1 - \sigma_3)^2 + (\sigma_2 - \sigma_3)^2}$ , psi

$p_a$  = normalizing stress (atmospheric pressure; in this case, 14.7 psi)

$k_1, k_2, k_3$  = regression coefficients

In other words, a given specimen is tested at 15 different stress states.  $\theta$ ,  $\tau_{oct}$ , and  $M_r$  are calculated from the data. Using the above model (Eq. 1), the regression constants  $k_1, k_2, k_3$  are determined for each specimen. A non-linear regression analysis procedure included in a statistical software package called SigmaStat® was

used for this portion of the work. Data used for the regressions are included in Appendix B

### Quality of the Testing Program

Per recommendations in the M-E PDG, regressions are performed on individual specimen data to evaluate the validity of the test. The M-E PDG recommendation is that the goodness-of-fit statistic,  $R^2$ , be at least 90% for each set of individual specimen tests (15 stress states, one specimen). Because  $R^2$  is not the most appropriate goodness-of-fit statistic when using non-linear regression techniques, the statistic  $S_e/S_y$  was also included in the results.  $S_e$  is the standard deviation of the residuals (the difference between the predicted and observed  $M_r$  values), and  $S_y$  is the standard deviation of the observed  $M_r$  values. Smaller  $S_e/S_y$  values indicate a better fit. Regression coefficients were also determined by pooling the data (45 sets of stress states [15 stress states per replicate specimen, three replicate specimens] and resulting  $M_r$  values) from all three replicates and fitting it to Eq. 1. The pooled regression coefficients will be used for comparison purposes in this section.

**Table 4: Summary of Results**

| Specimen and Statistics | Target Dry Unit Weight (pcf) | Target Moisture (%) | As-Compacted Moisture [7th lift] (%) | Actual Dry Density (pcf) | Actual Moisture (%) | Actual Saturation* (%) | $k_1$             | $k_2$ | $k_3$  | $R^2$ | $S_e/S_y$ |
|-------------------------|------------------------------|---------------------|--------------------------------------|--------------------------|---------------------|------------------------|-------------------|-------|--------|-------|-----------|
| Gasc A-D1               | 133.7                        | 9.4                 | 9.8                                  | 133.9                    | 8.9                 | 92.6                   | 1456.506          | 0.783 | -0.353 | 0.998 | 0.050     |
| Gasc A-D2               | 133.7                        | 9.4                 | 9.9                                  | 133.8                    | 8.8                 | 91.6                   | 1429.921          | 0.752 | -0.323 | 0.997 | 0.058     |
| Gasc A-D3               | 133.7                        | 9.4                 | 9.8                                  | 133.7                    | 8.9                 | 92.4                   | 1298.257          | 0.796 | -0.325 | 0.996 | 0.068     |
| Average                 |                              |                     | 9.8                                  | 133.8                    | 8.9                 | 92.2                   | Pooled Regression |       |        |       |           |
| St Dev.                 |                              |                     | 0.0828                               | 0.0647                   | 0.0491              | 0.5420                 | 1394.519          | 0.777 | -0.334 | 0.989 | 0.110     |
| Coeff. Var (%)          |                              |                     | 0.8424                               | 0.0484                   | 0.5511              | 0.5877                 |                   |       |        |       |           |
| Gasc O-G1               | 111.2                        | 6.0                 | 6.4                                  | 111.5                    | 5.6                 | 28.7                   | 1997.677          | 0.724 | -0.340 | 0.988 | 0.134     |
| Gasc O-G2               | 111.2                        | 6.0                 | 6.2                                  | 111.5                    | 5.6                 | 28.8                   | 1782.632          | 0.724 | -0.215 | 0.991 | 0.102     |
| Gasc O-G3               | 111.2                        | 6.0                 | 6.5                                  | 111.4                    | 5.6                 | 28.9                   | 2130.596          | 0.664 | -0.403 | 0.990 | 0.108     |
| Average                 |                              |                     | 6.4                                  | 111.5                    | 5.6                 | 28.8                   | Pooled Regression |       |        |       |           |
| St Dev.                 |                              |                     | 0.1165                               | 0.0603                   | 0.0265              | 0.0914                 | 1966.229          | 0.703 | -0.316 | 0.979 | 0.092     |
| Coeff. Var (%)          |                              |                     | 1.8302                               | 0.0541                   | 0.4725              | 0.3177                 |                   |       |        |       |           |
| BF A-D1                 | 138.0                        | 7.4                 | 7.2                                  | 138.2                    | 6.8                 | 86.1                   | 2044.140          | 0.632 | -0.320 | 0.994 | 0.086     |
| BF A-D2                 | 138.0                        | 7.4                 | 7.3                                  | 138.3                    | 6.8                 | 86.4                   | 2281.441          | 0.541 | -0.321 | 0.987 | 0.122     |
| BF A-D3                 | 138.0                        | 7.4                 | 7.3                                  | 138.3                    | 6.7                 | 85.9                   | 2098.281          | 0.610 | -0.328 | 0.988 | 0.120     |
| Average                 |                              |                     | 7.2                                  | 138.3                    | 6.8                 | 86.1                   | Pooled Regression |       |        |       |           |
| St Dev.                 |                              |                     | 0.0800                               | 0.0779                   | 0.0223              | 0.2767                 | 2139.855          | 0.594 | -0.322 | 0.985 | 0.125     |
| Coeff. Var (%)          |                              |                     | 1.1045                               | 0.0564                   | 0.3291              | 0.3213                 |                   |       |        |       |           |
| BF O-G1                 | 115.5                        | 3.9                 | 4.5                                  | 115.5                    | 3.7                 | 22.0                   | 3050.980          | 0.563 | -0.265 | 0.995 | 0.080     |
| BF O-G2                 | 115.5                        | 3.9                 | 4.0                                  | 115.6                    | 3.7                 | 21.8                   | 2741.661          | 0.637 | -0.304 | 0.995 | 0.080     |
| BF O-G3                 | 115.5                        | 3.9                 | 4.3                                  | 115.4                    | 3.6                 | 21.3                   | 2882.995          | 0.589 | -0.293 | 0.992 | 0.098     |
| Average                 |                              |                     | 4.3                                  | 115.5                    | 3.7                 | 21.7                   | Pooled Regression |       |        |       |           |
| St Dev.                 |                              |                     | 0.2296                               | 0.0531                   | 0.0537              | 0.3323                 | 2891.444          | 0.596 | -0.287 | 0.989 | 0.083     |
| Coeff. Var (%)          |                              |                     | 5.3978                               | 0.0460                   | 1.4531              | 1.5307                 |                   |       |        |       |           |

\*A-D Saturations based on CoreLok specific gravities; O-G Saturations based on T 85 results

Before performing the pooled regressions, variability among the replicate specimens of the Gasc O-G and BF O-G materials was analyzed using a one-way analysis of variance (ANOVA). Three parameters were analyzed relative to the effect that differences among the replicate specimens may have on them:  $M_r$ , deviator stress ( $\sigma_d$ ), and confining pressure ( $\sigma_3$ ). Table 5 shows the results of the basic ANOVA.

**Table 5: Replicate One-Way Anova**

| Material | $M_r$ vs. Replicate |           | $\sigma_d$ vs. Replicate |           | $\sigma_3$ vs. Replicate |           |
|----------|---------------------|-----------|--------------------------|-----------|--------------------------|-----------|
|          | p-value             | $R^2$ (%) | p-value                  | $R^2$ (%) | p-value                  | $R^2$ (%) |
| Gasc O-G | 0.921               | 0.39      | 1.000                    | 0.00      | 1.000                    | 0.00      |
| BF O-G   | 0.936               | 0.31      | 1.000                    | 0.00      | 1.000                    | 0.00      |

The higher the p-value is (1.000 is maximum; 0.000 is minimum) or the lower the  $R^2$  value is (1.000 is maximum; 0.000 is minimum), the lower the probability that the replicates are different. To verify that any differences between the  $M_r$  values (per stress state, per replicate) are strictly a function of the replicate specimen material conditions, the stress parameters ( $\sigma_d$  and  $\sigma_3$ ) were analyzed in regard to the replicates. In all cases, the differences in the  $\sigma_d$  and  $\sigma_3$  values were so small as to be completely insignificant, which makes sense, as these parameters are not really responses but computer-controlled inputs. Based on the p-values and  $R^2$  values, and comparing the two aggregates, the Gasc O-G aggregate possessed the most  $M_r$  variability between replicate specimens. However, the replicate  $M_r$  variability for both aggregates was highly insignificant at an alpha = 0.05 (95% confidence) level; i.e. the p-values for both were much greater than 0.05, meaning that the replicates were very similar per aggregate.

### Effect of Gradation on $M_r$

Looking only at  $k_1$  (the intercept or scaling factor for Eq. 1) from the pooled regressions in Table 4, one can see that, for both aggregates, the O-G aggregate  $k_1$  values were considerably higher than those of the corresponding A-D aggregate, indicating that the O-G material was much stiffer. A major factor in this increased stiffness is the much lower degree of saturation present in the O-G specimens relative to the A-D specimens. Haynes and Yoder (14) showed that 80-85% saturation was the general range at which the deflection (i.e. stiffness) properties of dense-graded base materials used in the AASHTO Road Test began to be severely affected. This is the primary advantage of open-graded base courses; provided they remain permeable, there is a practical upper limit to the degree of saturation thereby insuring long-lasting stability of the pavement structure.

Table 6 shows a comparison of the two materials in regard to  $M_r$  (as calculated by Eq. 1 and using the pooled regression coefficients) for a stress state of  $\theta = 12$  psi ( $\sigma_1 = 6$  psi,  $\sigma_2$  and  $\sigma_3 = 3$  psi each). For discussion purposes, Table 6 also includes  $M_r$  values reported in the previous MoDOT  $M_r$  study (1) that resulted from testing specimens with a higher fines content (W-F) created with a blend of as-delivered material (95%) and additional fines (5%).

**Table 6: Resilient Moduli at  $\theta = 12$  psi**

| Material      | Properties  | Gradations |       |       | $\Delta M_r$ (%)<br>[(O-G) – (A-D)] |
|---------------|-------------|------------|-------|-------|-------------------------------------|
|               |             | W-F        | A-D   | O-G   |                                     |
| Bethany Falls | $M_r$ (psi) | 22776      | 27071 | 36682 | +35.5                               |
|               | P200 (%)    | 17.6       | 13.8  | 0     |                                     |
| Gasconade     | $M_r$ (psi) | 17101      | 16980 | 24344 | +43.4                               |
|               | P200 (%)    | 14.2       | 10.7  | 0     |                                     |

As reported in the previous MoDOT  $M_r$  study (1), a decreased fines content had mixed effects: some materials experienced an increase in  $M_r$  (at a particular stress state) and some experienced a decrease in  $M_r$ . At  $\theta = 12$  psi, this is the case for the Gasconade and Bethany Falls material as reflected in Table 6: the Bethany Falls aggregate had a higher  $M_r$  with a reduction in fines while the Gasconade had a slightly lower  $M_r$  with a reduction in fines at elevated levels (i.e. when reducing P200 from 14.2 to 10.7%) that might be statistically insignificant. However, when the fines content was reduced to zero percent, a significant increase in  $M_r$  (relative to the A-D condition) occurred for both the Bethany Falls aggregate (35.5% increase) and the Gasconade aggregate (43.4% increase), again, for this particular stress state.

Figures 5 through 8 show the plots of  $M_r$  versus  $\theta$ , and  $M_r$  versus  $\tau_{oct}$  using the pooled data from the three replicate  $M_r$  tests per aggregate. The three series on each plot represent the three gradations that have been investigated in this and the previous MoDOT  $M_r$  study. As can be seen, in general, the trend is that as fines decrease from the W-F (14.2 -17.7% fines) to A-D (10.7 -13.8% fines) to O-G (zero fines), at a given stress state,  $M_r$  increases.

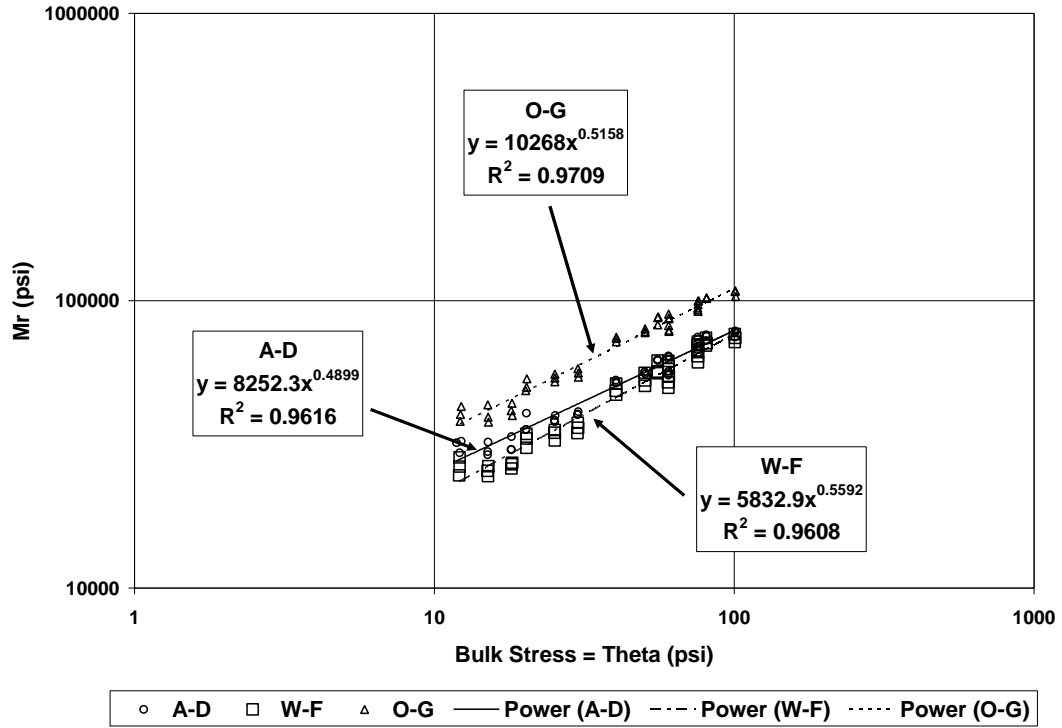


Figure 5: Bethany Falls; Pooled  $M_r$  vs  $\theta$ ; O-G, A-D, and W-F Gradations

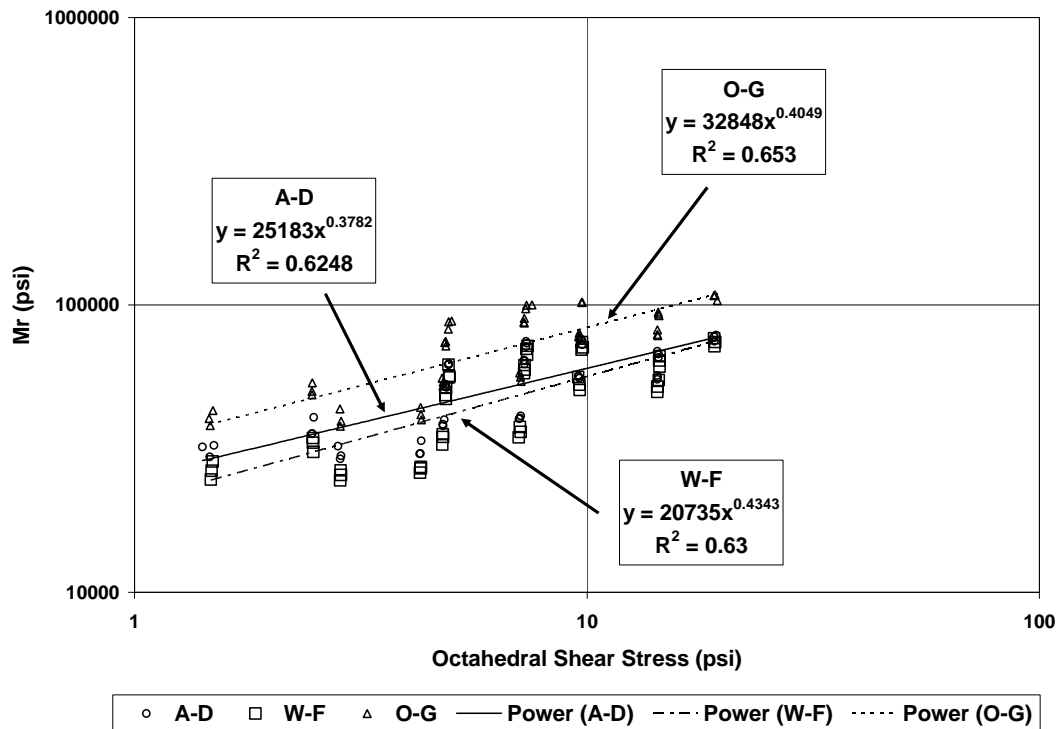


Figure 6: Bethany Falls; Pooled  $M_r$  vs  $\tau_{oct}$ ; O-G, A-D, and W-F Gradations

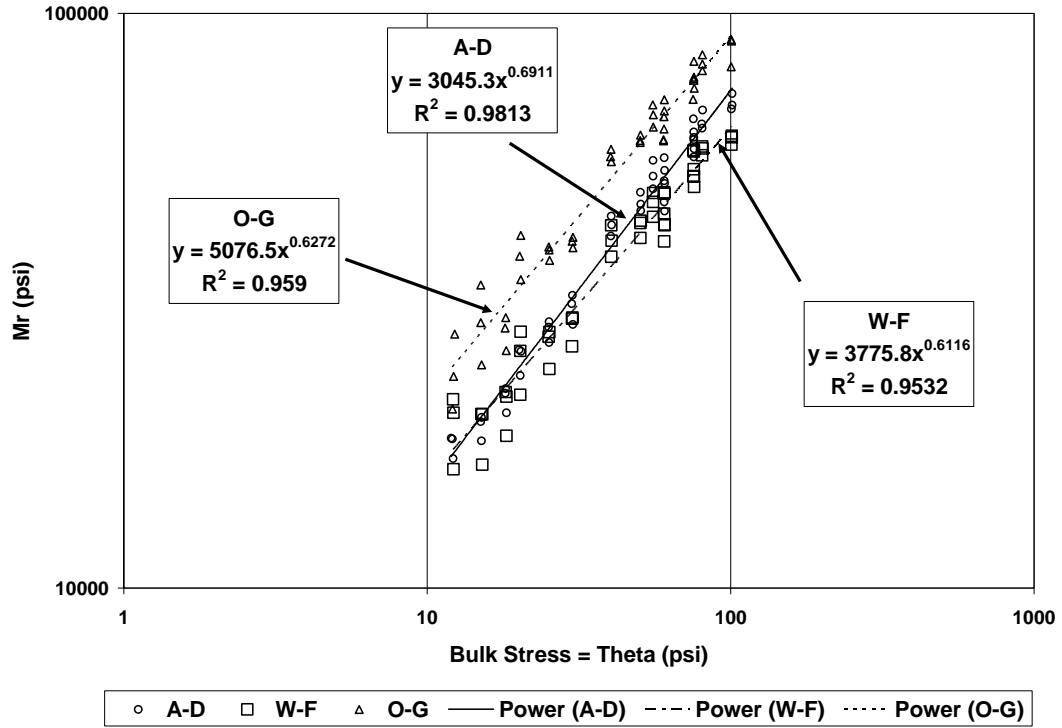


Figure 7: Gasconade; Pooled  $M_r$  vs  $\theta$ ; O-G, A-D, and W-F Gradations


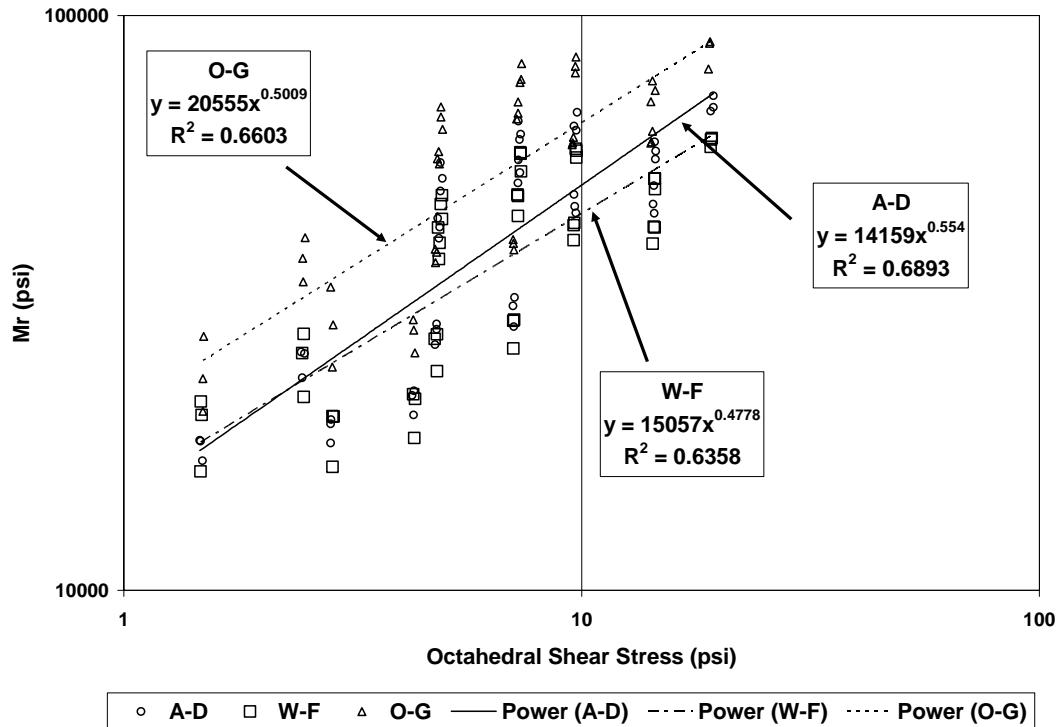


Figure 8: Gasconade; Pooled  $M_r$  vs  $\tau_{oct}$ ; O-G, A-D, and W-F Gradations

## Optimum Fines Content

Past studies have shown that there is an optimum amount of fines for maximum strength and stiffness of unbound granular base materials. Yoder and Witczak (15) showed an optimum range of 6 to 9% fines for maximum CBR. The National Crushed Stone Association classical study (16) of the effect of various parameters on triaxial shear strength reported optimums of 8 to 12%. For resilient modulus, Jorenby and Hicks (17) reported optimum fines around 5%. For the present study, it could be argued that the two fines contents tested in the two studies performed for MoDOT were on the low side (zero %) and the high side (11 and 14%) of what would have been the optimum. A plot of  $M_r$  versus P200 based on data in Table 6 is given in Figure 9.

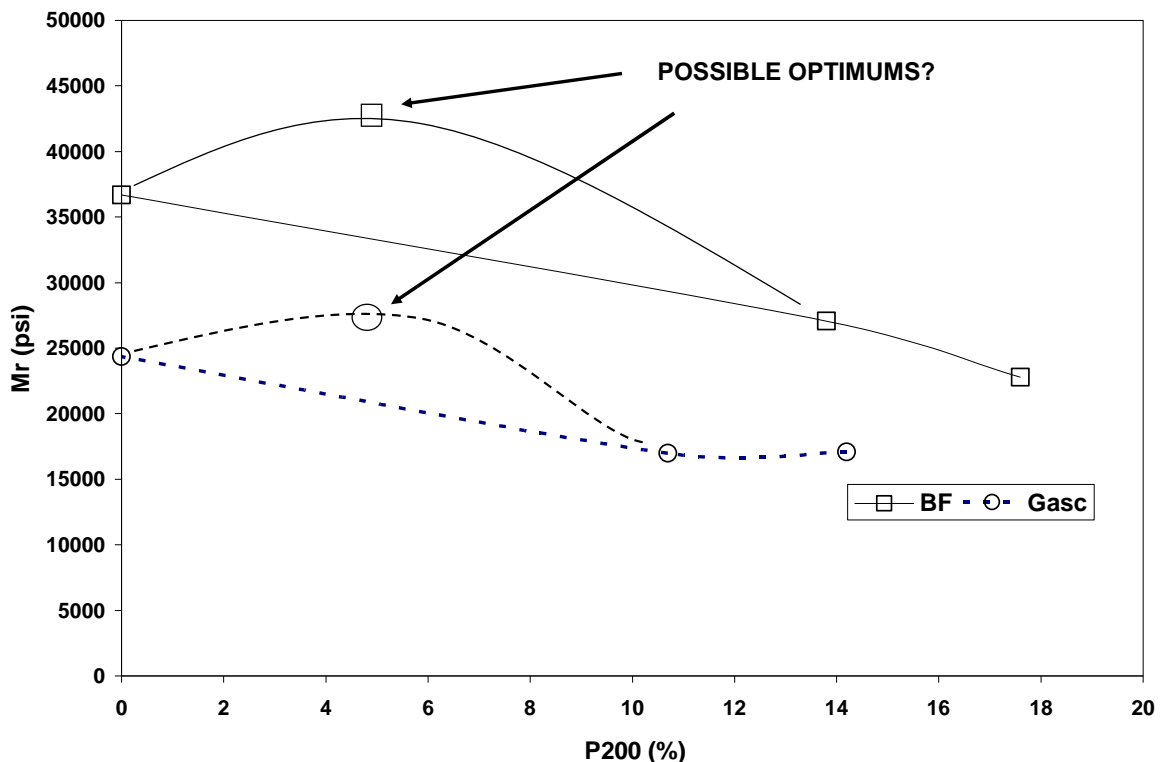

**Figure 9:  $M_r$  (at  $\theta = 12$  psi) versus P200**

As indicated in Figure 9, one could postulate that there may be an optimum fines content for a particular aggregate, with a particular overall gradation, a particular degree of saturation, and at a particular stress state that would produce the maximum  $M_r$  for such conditions. More testing on these aggregates is needed to address this question.

## Comparison to Past Studies

The issue of the effect of fines (and gradation in general) on  $M_r$  has been addressed in the literature review of a previous study for MoDOT by Richardson and Kremer (18), where it was reported that as fines content increases, resilient modulus decreases (19-22). There was some support of the idea that a high degree of saturation generated pore pressures which lowered  $M_r$  (19), thus explaining the reason why some open-graded mixtures have greater  $M_r$  values than dense-graded materials, although some studies showed the opposite (19, 22) or at least that gradation is of a negligible significance (23). Others, as noted above, report that an optimum fines content exists. More recent studies have shown a decrease in  $M_r$  upon an increase in fines from 6 to 12% (24). The Richardson and Kremer study itself reported that of the four aggregates tested, two showed an increase in  $M_r$  when moving from a dense gradation to an open gradation, one showed essentially no change, and one showed a decrease.

In a more recent literature review, Liang (25) cited Hicks and Monismith (26), Barksdale (19), Thom and Brown (23), Barksdale and Itani (27), Rada and Witczak (28), Knutson and Thompson (29), Raad, et al. (30), Thompson and Smith (22), Kamal, et al. (31), Tian, et al. (32), and Heydinger, et al. (33). The conclusions in the cited references varied in regard to the effect of fines content (or gradation in general) on  $M_r$ . Excerpts from Liang's literature review are inserted below:

Hicks and Monismith: Hicks and Monismith, among others, studied  $M_r$  by using the previously popular bulk stress model given as

$$M_r = k_1(\theta)^{k_2} \quad (2)$$

Where

- $M_r$  = resilient modulus, psi
- $\theta$  = bulk stress =  $\sigma_1 + \sigma_2 + \sigma_3$ , psi
- $k_1, k_2$ , = regression coefficients

Liang's comments are as follows:

"[Hicks and Monismith] indicated that the bulk stress model parameters  $k_1$  and  $k_2$  were affected by the fines content. The manner in which  $k_1$  changes depends on the aggregate type. For the partially crushed aggregate,  $k_1$  generally decreased as the fines content was increased. For the crushed aggregate, however,  $k_1$  increased with increasing fines content. The same trends were also observed for the partially saturated and saturated test series. For  $k_1$ , it appeared that it decreased slightly as fines content increased. They also found that  $k_1$  was always larger for the crushed aggregate than the partially crushed material, regardless of aggregate gradation."

Barksdale; Thom and Brown; Barksdale and Itani: According to Liang, these studies generally agreed with Hicks and Monismith:

“Their [Hicks and Monismith] test results seemed to agree with later studies [Barksdale; Thom and Brown; Barksdale and Itani] who observed a decrease in the value of resilient modulus as the fines content was increased.”

Rada and Witczak: Liang’s comments are as follows:

“On the other hand, [Rada and Witczak] found that the effect of aggregate gradation showed no general trend regarding the influence of fines (percentage pass No.200 sieve) on resilient modulus. For the angular base materials (DGA and CR-6 aggregate), there appeared to be little change in either  $k_1$  or  $k_2$  for P200 values in the range of 7-17%. For bank-run gravel, an optimum  $k_1$  value was apparently near the dense condition, and a marked decrease in  $k_1$  occurred as the P200 value increased. In contrast,  $k_2$  appeared to increase with an increase in fines content. Although no pronounced changes occurred in  $k_1$  and  $k_2$  for the base materials, increase in P200 beyond the 16-18 percent range would eventually lead to pronounced change in the  $M_R$  response of these materials.”

Knutson and Thompson: Knutson and Thompson studied railroad ballast, an open-graded aggregate. Liang’s comments are as follows:

“[Knutson and Thompson] found no difference in resilient modulus between an ASTM No. 4 and No. 5 very open graded railway ballast aggregate. The tested aggregate grading presented lower resilient moduli than conventional well-graded aggregate. The No. 4 and No. 5 ballast were practically insensitive to change in water content due to their high permeability.”

Raad, et al.: Liang’s comments are as follows:

“[Raad, et al.] found that the densest graded aggregate exhibit the highest  $M_R$  values, and the open graded aggregate has the lowest values. However, the saturated granular materials will develop excess pore water pressure under undrained conditions, which could lead to a decrease in  $M_R$  values. Open-graded aggregates are more resistant to pore water pressure buildup than are dense graded aggregate and therefore are less likely to induce damage in pavement under saturated conditions.”

Although the  $M_r$  test results in this study are contrary to the results cited in the above Raad, et al. excerpt, the commentary about pore water pressure is important to understand. Although T 307 is performed with the drainage lines open, this does not necessarily insure “drained” conditions within dense-graded specimens. Loading times in the  $M_r$  test are so quick that pore water pressure may not fully dissipate during the 0.1 second stress pulse thereby lowering the instantaneous vertical effective stress (i.e.  $\sigma'_d$ ) experienced by the specimen and, therefore, reducing the  $M_r$ . The likelihood of pore water pressure building in open-graded aggregates is, even for very short periods of time, much less than in dense-graded aggregates.

Thompson and Smith: Liang’s comments are as follows:

“[Thompson and Smith] reported that for gradations that differ only in the permissible amount passing sieve No.200, limited differences in  $M_R$  were noted among the various granular materials.”

Kamal, et al.: Liang's comments are as follows:

"[Kamal, et al.] found that resilient modulus will increase from the finer to the coarser mix and there is a slight increase in resilient modulus with increasing deviator stress. The resistance to shear and volumetric strains tends to increase from the finer to the coarser end of the proposed grading envelopes."

Tian, et al.: Liang's comments are as follows:

"[Tian, et al.] indicated that the coarse gradation limit will produce the highest resilient modulus."

Heydinger, et al.: Liang's comments are as follows:

"[Heydinger et al.] found that resilient modulus of aggregate was affected by aggregate gradation. They found that for limestone aggregate, the open graded specification had higher moduli than the dense graded specification. The moduli were highest for the upper gradation and lowest for the lower gradation for the Iowa mix. For gravel there was no strong trend for the variation of resilient moduli with respect to gradation."

As indicated in the previous excerpts, the effect of fines on  $M_r$  depends on other variables, some of which are not obviously evident. In the case of the two aggregates tested in this study, however, there is a definite increase in  $M_r$  with a reduction in fines from the levels present in the A-D gradations to the level present in the O-G gradation; i.e. no fines. However based on issues discussed in the literature review excerpts above, one must consider that the increase in  $M_r$  from the A-D condition to the O-G condition could be a function of the differences in the overall gradations, not just the difference in fines content.

## **Constructibility**

When contemplating the use of unbound, open-graded base courses, one must also consider how the material will behave under construction traffic. In general, as the fines content decreases, cohesion of the compacted aggregate also decreases. This poses the potential for significant disturbance or deformation of the compacted, unbound, open-graded base course as dump trucks, trimmers, pavers, etc. travel across it. In a sub-section of the 2003 Michigan special provision cited in the Technical Approach section of this report (7), the Michigan DOT addresses this issue of construction equipment travel on an open-graded base course as follows:

"Equipment Travel - Delete subsection 303.03.C of the Standard Specifications for Construction and replace with the following.

Equipment travel on the OGDC for placement of OGDC will be permitted provided that a minimum of 2 inches of additional OGDC aggregate is placed. All costs associated with placement of the additional aggregate and removal or trimming thereof will be borne by the Contractor. Any removed OGDC aggregate, which will be re-used on this or any MDOT

project, must be stockpiled and re-tested to verify the aggregate meets the specification requirements for the intended item of use.

Where no lateral space exists due to permanent physical obstructions, maintaining traffic requirements or other unavoidable conditions, concrete or Hot Mix Asphalt delivery to the paver via OGDC will be permitted provided that:

A. the specified in-place OGDC gradation is maintained and no other damage to the grade, subbase or subgrade occurs; and

B. varied truck routes or paths are used to minimize the potential for damage to the roadbed.

Correct all observed degradation to the OGDC resulting from equipment travel, according to subsection 303.02.E.2 of the Standard Specifications for Construction. Protect the underdrain system from damage at all entry and exit points.”

Wisconsin, too, writes into its specifications detailed instructions on constructing and maintaining base courses, both dense and open-graded (11):

#### “301.3.4 Constructing Base

##### 301.3.4.1 General

(1) Place aggregate in a manner that minimizes hauling on the subgrade. Do not use vehicles or operations that damage the subgrade or in-place base. Deposit material in a manner that minimizes segregation.

(2) Construct the base to the width and section the plans show. Shape, and compact the base surface to within 0.04 feet (12 mm) of the plan elevation.

(3) Ensure there is adequate moisture in the aggregate during placing, shaping, and compacting to prevent segregation and achieve adequate compaction.

(4) Maintain the base until paving over it, or until the engineer accepts the work, if paving is not part of the contract. The contractor is not responsible for maintaining material placed on detours, unless the special provisions specify otherwise.”

The issue of damage to unbound, open-graded base courses due to construction traffic is probably the reason many states have moved to or adopted asphalt or cement treated permeable bases. If unbound permeable bases are to be used, the trick is to specify a gradation that strikes a balance between stability and drainability. Table 7 shows the Michigan, Oregon, and Wisconsin open-graded aggregate gradation specification relative to MoDOT’s current and proposed Type 5 gradation specification, and the experimental gradation used for this study.

### **Comparison of Experimental Gradations to Other DOT Gradations**

The first thing one notices in Table 7 is the significantly smaller maximum allowable P200 that Michigan, Oregon, and Wisconsin specify relative to Missouri, the greatest being 6% *maximum* allowed by Michigan. In referring back to Figure 1, 6% is essentially the *minimum* P200 being produced in Missouri for a Type 5 base aggregate. Although the experimental gradation was built with washed aggregates and 0% fines, it is unrealistic to expect 0% fines in the crushed aggregates produced

in Missouri, and especially once they are in-place in the pavement structure. Even if one started with perfectly clean aggregate at the quarry, handling, trucking, dumping, shaping, and compacting the base material would generate significant fines.

**Table 7: Various State Specifications for Open-Graded Aggregates**

| Sieve Size<br>(mm) Standard |                 | States and Gradation Specifications (% Passing) |        |           |          |       |              |
|-----------------------------|-----------------|---|--------|-----------|----------|-------|--------------|
|                             |                 | Michigan  | Oregon | Wisconsin | Missouri |       | Experimental |
| Current Type 5              | Proposed Type 5 |   |        |           |          |       |              |
| 37.5                        | 1.5"            | 100   |        |           |          |       |              |
| 25.0                        | 1"              |   | 100    | 90-100    | 100      | 100   | 100.0        |
| 19.0                        | 3/4"            | 60-80   | 80-98  |           |          |       | 96.0         |
| 12.5                        | 1/2"            | 35-65   | 60-85  |           | 60-90    | 60-90 | 80.0         |
| 9.50                        | 3/8"            |   | 30-65  | 45-65     |          |       | 69.0         |
| 4.75                        | #4              |   |        | 15-45     | 35-60    | 25-60 | 25.0         |
| 2.36                        | #8              | 10-25   |        |           |          |       | 18.3         |
| 2.00                        | #10             |   | 5-20   | 0-20      |          |       |              |
| 1.18                        | #16             |   |        |           |          |       | 11.6         |
| 0.600                       | #30             | 5-18  |        |           | 10-35    | 5-35  | 5.0          |
| 0.425                       | #40             |   | 0-6    | 0-10      |          |       |              |
| 0.300                       | #50             |   |        |           |          |       | 3.3          |
| 0.150                       | #100            |   | 0-3*   |           |          |       | 1.6          |
| 0.075                       | #200            | 0-6   |        | 0-5.0     | 0-15     | 0-15  | 0.0          |

\* Dry Sieved Basis

Another interesting observation in Table 7 is that Wisconsin has the greatest number of control sieves on the finer side of the gradation spectrum (#4 to #200, inclusive). It has been argued that it is the mid-sized fine aggregate fractions (say, #8 to #40) that really contribute to establishing the balance between stability and drainability. Having a relatively well-graded particle distribution, especially in the mid-sized sands range, helps with aggregate interlock and thereby increases stability while, at the same time, limiting the fines content contributes to increased drainability.

In looking again at the experimental gradation used in this study, one notices that the size fraction dominating the overall particle size distribution is that aggregate fraction passing the 3/8" sieve and retained on the #4; 44% of the entire gradation falls in this narrow fraction. This is mostly a function of choosing to build the gradation in such a way as to isolate the effects of the proposed gradation change on the  $M_r$  of the material to the finer side of the gradation. However, the particle distribution of the material passing the #4 correlates fairly well with the specifications of the other three states. Although permeability testing was not in the scope of this investigation, one could argue that the permeability of the experimental gradation would approach that of the open-graded aggregates specified by the other states.

It should be noted that the  $M_r$  specimens built to the experimental O-G gradation required compactive effort comparable to the stiffest A-D specimens and the particle size distribution throughout the  $M_r$  specimens remained visibly homogenous. The

non-segregation of aggregate particles during vibratory compaction is believed to be the result of compacting at a moisture content ~2% greater than the absorption of the aggregate thereby providing sufficient, but not excessive, moisture to bind the finer particles to the coarser particles. However, the almost total lack of cohesion of the aggregate particles was apparent during scarification of each lift after vibratory compaction. When scarifying the A-D  $M_r$  specimens during the previous MoDOT  $M_r$  study (1), a stainless steel laboratory spatula had to be used for scarifying (cutting) the top of each lift prior to compaction of the successive lift (per T 307) because the surface of the lift was hard and bound tightly. When scarifying each lift of the O-G  $M_r$  specimens, a rubber tipped kitchen spatula was used to lightly disturb the surface of each lift, which came apart with very little effort. This demonstrated the issue discussed earlier about the problem of stability (or maybe better defined as fragility) of the open-graded material under construction equipment.

## CONCLUSIONS

Based on the results of the testing performed for this investigation, limited as it was, one can conclude the following:

- $M_r$  results in this study (coarser, lower percent fines gradation) increased when compared to test results from the previous MoDOT  $M_r$  study in which the same aggregates were tested but typical Type 5 gradations (denser, higher fines) were investigated. A major factor in the increased  $M_r$  most likely was the lower degree of saturation present in the relatively open-graded specimens of this study in comparison to the dense-graded specimens examined in the previous study.
- For those aggregate producers that could benefit from the proposed specification change, it seems likely that fewer fines would be generated during production thereby increasing the probability of a more drainable base aggregate.
- Constructibility is of concern. However, compacting open-graded aggregates at a moisture content ~2% above absorption 1) provides sufficient particle surface moisture for compaction lubrication purposes and for binding the finer particles to the coarser particles through apparent cohesion (i.e. high negative pore pressure caused by small menisci radii) thereby reducing the probability of dry-aggregate segregation, but 2) limits excess water that could hinder maximum densification or flush the finer fractions during compaction (i.e. segregate the particles).

## RECOMMENDATIONS – FUTURE RESEARCH

- If drainability is still the main purpose for specifying a Type 5 base aggregate, *consideration should be given to lowering the maximum percentage passing on certain control sieves*. Aggregate producers could possibly generate this material by blending two (or more) lower-quality aggregates already in production.
- The concept of compaction of open-graded aggregates at a moisture content ~2% above absorption needs more study.
- To better characterize the change in  $M_r$  that the proposed Type 5 gradation specification will cause,  $M_r$  tests should be performed along the lower bounds of the current Type 5 specification.
- As  $M_r$  tests might not be the best measure of determining the effects of the change in the Type 5 gradation specification on pavement performance, thus other types of tests (e.g. triaxial shear, CBR, cyclic total deformation) should be investigated.
- More  $M_r$  testing is required to determine the optimum fines content for particular aggregates under particular conditions. Regression equations could be developed to determine those fines content levels that would maximize  $M_r$ .

## REFERENCES

1. Richardson, D. N., Petry, T., Ge, Y., Han, Y., Lusher, S. M., *Resilient Moduli of Typical Missouri Soils and Unbound Granular Base Materials*, Final Report for Missouri DOT Project RI06-001. Prepared by Missouri University of Science & Technology, Department of Civil, Architectural, and Environmental Engineering, Rolla, Missouri. 2008.
2. *Determining the Resilient Modulus of Soils and Aggregate Materials*, in AASHTO T 307-99 (2003). American Association of State Highway and Transportation Officials, Washington, D.C. 2003.
3. *Specific Gravity and Absorption of Coarse Aggregate*, in AASHTO T 85-91 (2000). American Association of State Highway and Transportation Officials, Washington, D.C. 2000.
4. *ASTM Standard Test Methods for Maximum Index Density and Unit Weight of Soils Using a Vibratory Table*, D 4253-00 (Reapproved 2006), American Society of Testing Materials, West Conshohocken, PA. 2006.
5. *Moisture Density Relations of Soils Using a 2.5-kg (5.5-lb) Rammer and a 305-mm (12-in.) Drop*, in AASHTO T 99-01. American Association of State Highway and Transportation Officials, Washington, D.C. 2001.
6. White, D. J., Vennapusa, P., Jahren, C. T. *Determination of the Optimum Base Characteristics for Pavements*. Final Report for Iowa DOT Project TR-482. Prepared by Center for Transportation Research and Education (CTRE Project 02-119), Iowa State University, Ames, Iowa. May 2004. Website accessed September 22, 2008, <http://www.ctre.iastate.edu/reports/tr482.pdf>
7. Michigan Department of Transportation, *Special Provision for Open-Graded Drainage Course, Modified*; O3SP303(A), FHWA:APPR:02-07-06. Website accessed September 22, 2008, [http://mdotwas1.mdot.state.mi.us/public/dessssp/spss\\_source/O3SP303A.pdf](http://mdotwas1.mdot.state.mi.us/public/dessssp/spss_source/O3SP303A.pdf)
8. Michigan Department of Transportation, *2003 Standard Specifications for Construction*, Section 303: Open-Graded Drainage Courses. Website accessed September 22, 2008, <http://mdotwas1.mdot.state.mi.us/public/specbook/>
9. Oregon Department of Transportation, *2008 Standard Specifications*, Section 00641: Aggregate Subbase, Base, and Shoulders. Website accessed September 22, 2008, [http://www.oregon.gov/ODOT/HWY/SPECS/docs/08book/08\\_00600.pdf](http://www.oregon.gov/ODOT/HWY/SPECS/docs/08book/08_00600.pdf)
10. Ohio Department of Transportation, *2008 Construction and Materials Specifications*, Supplement 1015: Compaction of Unbound Materials; Effective 4/21/2006. Website accessed September 22, 2008. [http://www.dot.state.oh.us/Divisions/ConstructionMgt/Specification%20Files/1015\\_04212006\\_for\\_2008.PDF](http://www.dot.state.oh.us/Divisions/ConstructionMgt/Specification%20Files/1015_04212006_for_2008.PDF)
11. Wisconsin Department of Transportation, *2008 Standard Specifications*, Section 301.3.4.2: Standard Compaction. Website accessed September 22, 2008, <http://roadwaystandards.dot.wi.gov/standards/stdnspec/sect301.pdf>

12. Wisconsin Department of Transportation, *Construction and Materials Manual*, Procedure 4-15-32: Appendix A: Permeability Apparatus and Procedure. Website accessed September 22, 2008.  
<http://roadwaystandards.dot.wi.gov/standards/cmm/4-15-32.pdf>
13. *Guide for Mechanistic-Empirical Design of New and Rehabilitated Pavement Structures*, Part 2, Chapter 2, Materials; page 2.2.66. Website accessed September 22, 2008. [http://www.trb.org/mepdg/Part2\\_Chapter2\\_Materials.pdf](http://www.trb.org/mepdg/Part2_Chapter2_Materials.pdf)
14. Haynes, J.H. and E.J. Yoder, *Effects of Repeated Loading on Gravel and Crushed Stone Base Course Materials Used in the AASHO Road Test*. Highway Research Record, No. 39. 1963. p. 82-96.
15. Yoder, E.J. and M.W. Witzczak, *Principles of Pavement Design*, 2<sup>nd</sup> ed., Wiley and Sons, 1975, 711 p.
16. Gray, J. E., *Characteristics of Graded Aggregate Base Course Aggregates Determined by Triaxial Tests*, National Crushed Stone Association Engineering Bulletin No. 12, Washington, D.C., 1962.
17. Jorenby, B. N., and R. G. Hicks, *Base Course Contamination Limits*, Transportation Research Record No. 1095. 1986. pp 86-101.
18. Richardson, D.N. and P.A. Kremer, *Determination of AASHTO Layer Coefficients: Volume II: Unbound Granular Bases and Cement Treated Bases*. University of Missouri-Rolla, Department of Civil Engineering, Rolla, Missouri. 1994.
19. Barksdale, R. D., *Laboratory Evaluation of Rutting in Base Course Materials*, In Proceedings of the Third International Conference on Structural Design of Asphalt Pavements, London, England, 1972, pp 161-174.
20. Barksdale, R.D., S.Y. Itani, and T.E. Swor, *Evaluation of Recycled Concrete, Open-Graded Aggregate, and Large Top-Size Aggregate Bases*, Transportation Research Record No. 1345. 1992. p. 92-100.
21. Barker, W. R., and R. C. Gunkel, *Structural Evaluation of Open-Graded Bases for Highway Pavements*, Miscellaneous Paper GL-79-18, U.S. Corps of Engineers, WES. 1979. 82 p.
22. Thompson, M. R., and K. L. Smith, *Repeated Triaxial Characterization of Granular Bases*, Transportation Research Record No. 1278. 1990. pp 7-17.
23. Thom, N. H., and S. F. Brown, *The Effect of Moisture on the Structural Performance of a Crushed Limestone Road Base*, Annual Transportation Research Board Meeting, Washington, D. C. 1987.
24. Thornton, S. I., and R. P. Elliott, *Fines Content of Granular Base Materials*, Final Report for Arkansas DOT (Report No. FHWA/AR-89/003). Prepared by Arkansas Highway and Transportation Center, Fayetteville, Arkansas. 1988.
25. Liang, R., *Evaluation of Drainable Bases Under Asphalt Pavement*, Final Report for Ohio DOT (Report No. FHWA/OH-2007/10). Prepared by University of Akron, Dept. of Civil Engineering, Akron, Ohio. May 2007. Website accessed September 22, 2008.  
<http://www2.dot.state.oh.us/research/2007/Pavements/14804-FR.pdf>
26. Hicks, R. G. and C. L. Monismith, *Factors Influencing the Resilient Response of Granular Materials*, Transportation Research Record No. 345. 1971. pp 15-30.

27. Barksdale, R. D., and S. Y. Itani, *Influence of Aggregate Shape on Base Behavior*, Transportation Research Record No. 1227. 1990. pp 173-182.
28. Rada, G., and M. W. Witczak, *Comprehensive Evaluation of Laboratory Resilient Moduli Results for Granular Material*, Transportation Research Record No. 810. 1981. pp 23-33.
29. Knutson, R. M., and M. R. Thompson, *Resilient Response of Railway Ballast*, Transportation Research Record, No. 651. 1978. pp 31-39.
30. Raad, L., Minassian, G. H., Gartin, S., *Characterization of Saturated Granular Bases Under Repeated Loads*, Transportation Research Record No. 1369. 1992. pp 73-82.
31. Kamal, M. A., Dawson, A. R., Garouki, T., Hughes, D. A. B., Shaa'at, A. A., *Field and Laboratory Evaluation of the Mechanical Behavior of Unbound Granular Materials in Pavements*, Transportation Research Record No. 1406. 1993. pp 88-97.
32. Tian, P., Zaman, M. M., Laguros, J. G., *Gradation Effects on Resilient Moduli of Aggregate Bases*, Transportation Research Record No 1619. 1998. pp 75-84.
33. Heydinger, A. G., Xie, Q., Randolph, B. W., Gupta, J. D., *Analysis of Resilient Modulus of Dense- and Open-Graded Aggregates*, Transportation Research Record No. 1547. 1996. pp 1-6.

## APPENDIX A

In the latest on-line-available specifications, special provisions, supplements, etc., Michigan, Oregon, and Wisconsin (and there could be more) do specify unbound, open-graded, permeable bases in pavement construction. An excerpt from a 2003 Michigan special provision (7) is as follows:

“c. Construction. Construct the open-graded drainage course (OGDC) according to Section 303 of the Standard Specifications for Construction with the following modifications.

1. Placement and Compaction - Place and compact a control strip as specified in section (c.3.A) of this Special Provision to establish a placement and rolling pattern that will achieve at least 95 percent compaction. If a thickness greater than 8 inches is specified, place the OGDC in two approximately equal lifts. Compact each layer to not less than 95 percent of its maximum unit weight. Finish the surface of the OGDC as specified in subsection 303.03.B of the Standard Specifications for Construction.”

This particular sub-section of the special provision does not indicate the test method to use to determine maximum dry unit weight. Referring to Section 303 of the Standard Specifications for Construction (8) in hopes of finding guidance on how to determine maximum unit weight yielded the following:

“303.03 Construction.

A. Preparation. Furnish and install the separation treatment, as specified on the plans, between the OGDC and the subbase.

B. Placement and Compaction. Place open-graded aggregate according to subsection 302.03 except that the density requirements are replaced by the following. Compact the open-graded aggregate with three complete passes of a minimum 10-ton, steel drum tandem roller. One complete pass will be down and back in the same path.”

So, assuming special provisions supersede standard specifications, it seems Michigan has replaced a compaction method based on roller-type and roller patterns to a percent compaction determination, but has not clearly specified how to determine the reference or maximum dry unit weight.

Oregon and other states also use the roller-type and roller-pattern method of compacting unbound, open-graded aggregates. An excerpt from Oregon’s 2003 Standard Specifications Section 00641 (9) is as follows:

“00641.44 Shaping and Compacting:

(a) Aggregate Base Courses:

(1) Dense-graded Aggregates - Begin compaction of each layer of dense-graded aggregates immediately after the material is spread and continue until a density of not less than 100% of the maximum density has been achieved when tested according to the MFTP.

(2) Open-graded Aggregates - Compact the surface of each layer of open-graded aggregates using rollers conforming to 00641.24. Roll until there is no appreciable reaction or yielding under the compactor.”

















